

Carlisle Intensive Growth Media Analysis

Results on a dry weight basis unless specified otherwise


| Analysis | Units | Result | FLL Reference Values |
|--|--------------------|---------------|-----------------------------|
| Particle Size Distribution (See accompanying report) < 0.05 mm (FLL ¹ reference value based on < 0.06 mm) | mass % | 11.0 | < 20 |
| Density Measurements | | | |
| Bulk Density (dry weight basis) | g/cm ³ | 0.67 | |
| Bulk Density (dry weight basis) | lb/ft ³ | 41.64 | |
| Bulk Density (at max. water-holding capacity) | g/cm ³ | 1.19 | |
| Bulk Density (at max. water-holding capacity) | lb/ft ³ | 74.41 | |
| Water/Air Measurements | | | |
| Moisture (as received basis) | mass % | 16.9 | |
| Total Pore Volume | Vol. % | 74.1 | |
| Maximum water-holding Capacity | Vol. % | 53.2 | > 45 |
| Air-Filled Porosity (at max water-holding capacity) | Vol. % | 20.9 | > 10 |
| Water permeability (saturated hydraulic conductivity) | cm/s | 0.02 | > 0.005 |
| Water permeability (saturated hydraulic conductivity) | in/min | 0.38 | > 0.0118 |
| pH and Salt Content | | | |
| pH (CaCl ₂) | | 6.1 | 5.5 - 8.0 |
| Soluble salts (water, 1:10, m:v) | mmhos/cm | 0.25 | |
| Soluble salts (water, 1:10, m:v) | g (KCl)/L | 1.07 | < 2.5 |
| Organic Measurements | | | |
| Organic matter content | mass % | 9.3 | < 12.0 |
| Nutrients | | | |
| Phosphorus, P2O5 (CAL) | mg/L | 85.0 | < 200 |
| Potassium, K2O (CAL) | mg/L | 471.0 | < 700 |
| Magnesium, Mg (CaCl ₂) | mg/L | 85.1 | < 160 |
| Nitrate + Ammonium (CaCl ₂) | mg/L | 5.7 | < 80 |

¹Forschungsgesellschaft Landschaftsentwicklung Landschaftsbau (FLL)
Guidelines for the Planning, Execution and Upkeep of Green-Roof Sites

Green Roof Media Particle Size Distribution

| Particle Size Analysis | | Sum of particles less than size specified | | | | |
|------------------------|------|---|------------------|------------|--------------------|--|
| Diameter -mm- | % | Diameter -mm- | Diameter -in- | Sieve size | % sum of particles | |
| < 0.002 | 2.4 | < 0.002 | --- | --- | 2.4 | |
| 0.002-0.05 | 8.6 | < 0.05 | --- | --- | 11.0 | |
| 0.05-0.25 | 6.5 | < 0.25 | 0.0098 | 60 mesh | 17.5 | |
| 0.25-1.0 | 13.4 | < 1.0 | 0.0394 | 18 mesh | 30.9 | |
| 1.0-2.0 | 16.2 | < 2.0 | 0.0787 | 10 mesh | 47.1 | |
| 2.0-3.2 | 16.8 | < 3.2 | 0.125 | 1/8 inch | 63.9 | |
| 3.2-6.3 | 23.9 | < 6.3 | 0.250 | 1/4 inch | 87.8 | |
| 6.3-9.5 | 10.6 | < 9.5 | 0.375 | 3/8 inch | 98.4 | |
| 9.5-12.5 | 1.6 | < 12.5 | 0.500 | 1/2 inch | 100.0 | |
| > 12.5 | 0.0 | | | | | |

FLL¹ Particle Size Distribution Graph for Intensive Systems

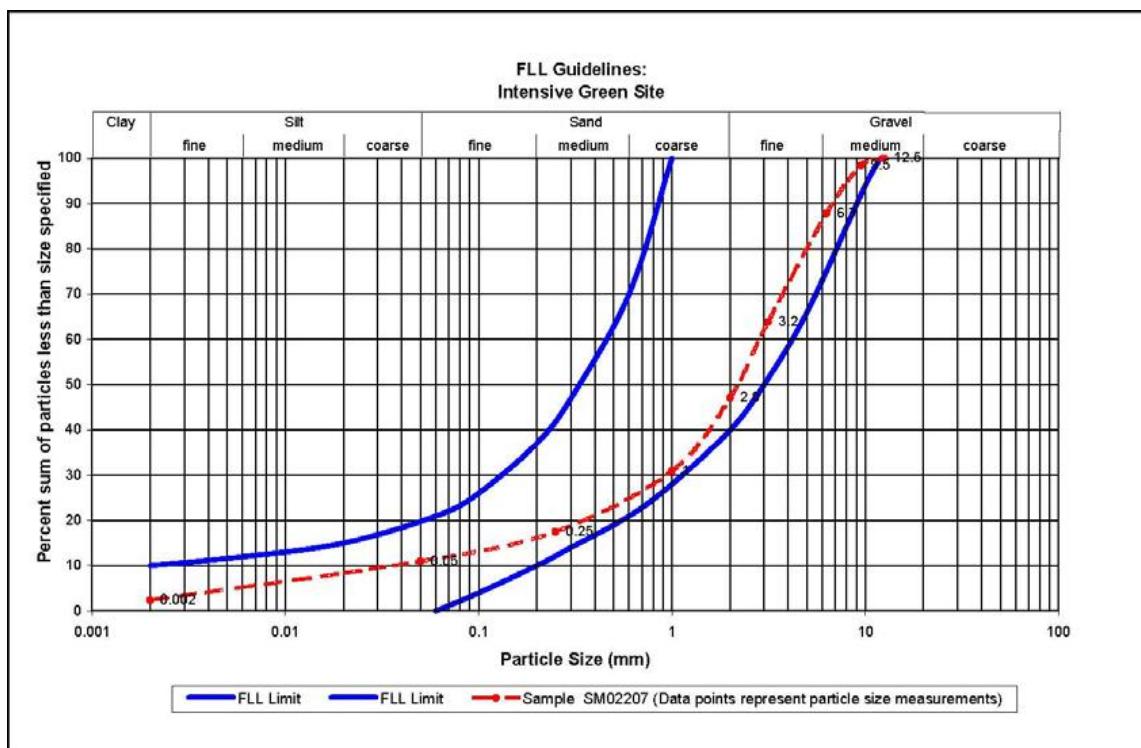

¹ Forschungsgesellschaft Landschaftsentwicklung Landschaftsbau (FLL). 2007. Guidelines for the Planning Execution and Upkeep of Green-Roof Sites